

Pseudogap Induced by Superconducting Fluctuation in the d - p Model

Akito KOBAYASHI^{1,2}, Atsushi TSURUTA¹, Tamifusa MATSUURA¹ and Yoshihiro KURODA^{1,2},

¹*Department of Physics, Nagoya University, Nagoya 464-01*

²*CREST, Japan Science and Technology Corporation (JST)*

(Received)

Using the d - p model, we demonstrate that the pseudogap, which is induced by the superconducting fluctuation, plays key roles in the determination of the phase diagram observed in high- T_c superconducting materials. We take the pairing interaction mediated by the spin fluctuation and calculate the superconducting transition temperature T_c , the NMR relaxation rate $1/T_1$ and the single-particle spectrum by treating both the superconducting fluctuation and spin fluctuation in a consistent fashion. As temperature decreases, $1/T_1T$ increases at high temperatures, and it reaches a maximum followed by a sharp drop in the underdoped region, due to the evolution of the pseudogap in the single-particle spectrum. The evolution is also consistent with those of ARPES experiments.

KEYWORDS: pseudogap, NMR relaxation rate, superconductivity, superconducting fluctuation, spin fluctuation, superexchange interaction, d - p model, $1/N$ -expansion, slave-boson technique

In the high- T_c superconductors, various anomalous properties have been observed at higher temperatures than the superconducting transition temperature T_c , especially in the underdoped region. Key issues on these anomalous properties must be on the existence of the pseudogap which has been suggested based on various experiments.^{1, 2, 3, 4, 5, 6, 7, 8, 9} In-plane resistivities,³ Hall coefficients⁴ and static uniform spin susceptibilities⁵ show peculiar temperature dependences below a certain characteristic temperature T_0 ,⁶ where the pseudogap is believed to become appreciable. Recently, photoemission experiments have revealed that the pseudogap is of the same size and has the same $\mathbf{k}$ -dependence as the superconducting gap.^{7, 8} More recently, the temperature evolution of the pseudogap has been observed by the angle-resolved photoemission spectroscopy (ARPES).⁹

There are several different views regarding the origin of the pseudogap. For example, it may be interpreted as a spin-excitation gap in the singlet RVB states obtained in the t - J model,^{10, 11} or it may be due to the Bose condensation of bound pairs^{12, 13} or due to superconducting fluctuations^{14, 15, 16, 17}.

In the present study, we demonstrate, using the d - p model, that the pseudogap induced by the superconducting fluctuation (SC fluctuation) plays key roles in the determination of the phase diagram observed in high- T_c superconducting materials. The pairing interaction is derived from the antiferromagnetic spin fluctuation (AF fluctuation) induced by the superexchange interaction J_s , while the AF fluctuation is suppressed by the pseudogap in the single-particle spectrum induced by the SC fluctuation. Thus, we must treat the effects of both the SC fluctuation and the AF fluctuation in a consistent fashion. Thus, we calculate the superconducting transition temperature T_c , the NMR relaxation rate $1/T_1$ and the single-particle spectrum. T_c has a maximum at the

hole-doping rate $\delta \cong 0.11$. At high temperatures, $1/T_1T$ increases as T decreases, due to the development of the AF fluctuation. We assign T_0 as a temperature at which the effects of the AF fluctuation begin to be appreciable. Then this T_0 corresponds to that determined by experiments on the Hall coefficient R_H .⁴ As the temperature decreases further, $1/T_1T$ reaches a maximum at a certain temperature, denoted by T_{sg} , for $\delta < 0.11$, followed by a sharp drop at $T \lesssim T_{sg}$. These features are consistent with the results of NMR experiments.^{1, 2} The plots of these three characteristic temperatures, T_c , T_0 and T_{sg} , as functions of δ , account for essential features of the phase diagram of the high- T_c superconducting materials. The single-particle spectral weights at the Fermi level decrease near the $[\pi, 0]$ and $[0, \pi]$ directions as T decreases at $T \lesssim T_0$, and eventually the Fermi surface survives only near the $[\pi, \pi]$ direction at $T \lesssim T_{sg}$. These features are consistent with the results of ARPES experiments.⁹

First, we describe our model and formulation. We take the simplest version of the d - p model as

$$H = \varepsilon_p \sum_{m=1}^N \sum_{\mathbf{k}_m} c_{\mathbf{k}_m m}^+ c_{\mathbf{k}_m m} + \varepsilon_d \sum_{m=1}^N \sum_i d_{im}^+ d_{im} + N_L^{-\frac{1}{2}} \sum_{m=1}^N \sum_{\mathbf{k}_m, i} \{t_i(\mathbf{k}_m) c_{\mathbf{k}_m m}^+ d_{im} b_i^+ + h.c.\}, \quad (1)$$

which is treated within the physical subspace where local constraints

$$\hat{Q}_i \equiv \sum_{m=1}^N d_{im}^+ d_{im} + b_i^+ b_i = 1 \quad (i = 1, 2, \dots, N_L) \quad (2)$$

hold. In the above, $c_{\mathbf{k}_m m}$, d_{im} and b_i are annihilation operators for a p -hole, a d -hole and a slave bo-

son, respectively, and $t_i(\mathbf{k}) = t_{\mathbf{k}} \exp(-i\mathbf{k} \cdot \mathbf{R}_i)$, where $t_{\mathbf{k}} \equiv 2t[1 - \frac{1}{2}(\cos k_x a + \cos k_y a)]^{\frac{1}{2}}$ and a is the lattice constant. The suffix m represents the spin-orbital degeneracy ($m = 1, 2, \dots, N$) introduced by dividing the phase space for $\mathbf{k}$ into $N/2$ subspaces for $\mathbf{k}_m$, keeping the total degrees of freedom for spins and orbitals unchanged as $\sum_{\sigma, \mathbf{k}} = \sum_{m, \mathbf{k}_m}$.¹⁸⁾ For numerical calculations in the present study, we set $N = 2$. The local constraints in eq. (2) are strictly held when we calculate an expectation value of a physical quantity.^{19,20)}

A set of self-consistent equations for single-particle Green's functions of the leading order in the $1/N$ -expansion was solved to yield the p -hole Green's function given by^{21,22)}

$$G(\mathbf{k}, i\varepsilon_n) = \sum_{\gamma=\pm} \frac{A_{\mathbf{k}}^{\gamma}}{i\varepsilon_n - E_{\mathbf{k}}^{\gamma}}, \quad (3)$$

with

$$E_{\mathbf{k}}^{\gamma} \equiv \frac{1}{2} \left(\varepsilon_p + \omega_0 + \gamma \sqrt{(\varepsilon_p - \omega_0)^2 + 4b t_{\mathbf{k}}^2} \right), \quad (4)$$

$$A_{\mathbf{k}}^{\gamma} \equiv \gamma \frac{E_{\mathbf{k}}^{\gamma} - \omega_0}{E_{\mathbf{k}}^{+} - E_{\mathbf{k}}^{-}}, \quad (5)$$

where ω_0 and b are the energy and the residue of the pole in the slave-boson Green's function. The chemical potential μ is determined by

$$n = 1 + \delta = \frac{1}{N_L} \sum_{\mathbf{k}\sigma\gamma} f(E_{\mathbf{k}}^{\gamma}), \quad (6)$$

where n and δ are the total hole number and the doped-hole number per unit cell, respectively, and $f(E) = [\exp\{E/k_B T\} + 1]^{-1}$. Here, it is noted that the solution $E_{\mathbf{k}}^{\pm}$ denotes the in-gap state emerging inside the charge transfer gap, $\Delta \equiv \varepsilon_p - \varepsilon_d$, upon doping carriers to a Mott insulator. The band width of the in-gap states is proportional to δ in the underdoped region. The effects of the interactions among the in-gap states are of higher-order terms in the $1/N$ -expansion.^{23,24,25,26,27,28,29)} Recently, it has been shown that quasi-particle interactions via the superexchange interaction play dominant roles in underdoped systems.³⁰⁾

Now, we derive coupled equations to treat the effects of the SC fluctuation and the AF fluctuation in a consistent fashion (termed the extended self-consistent t -matrix approximation). The pairing interaction mediated by the AF fluctuation via the superexchange interaction J_s in RPA is given by³¹⁾

$$V(\mathbf{q}) \cong \frac{J_s(\mathbf{q})}{1 - J_s(\mathbf{q})\chi_s^{(0)}(\mathbf{q}, 0)}, \quad (7)$$

with $J_s(\mathbf{q}) = -J_s(\cos(q_x) + \cos(q_y))$,

$$\chi_s^{(0)}(\mathbf{q}, \omega + i0^+) \cong \frac{b^2}{N_L} \sum_{\mathbf{k}} \frac{t_{\mathbf{k}+\mathbf{q}}^2 t_{\mathbf{k}}^2}{(E_{\mathbf{k}+\mathbf{q}}^- - \omega_0)^2 (E_{\mathbf{k}}^- - \omega_0)^2} \times \frac{1}{\pi} \int_{-\infty}^{\infty} dx f(x) \times [\text{Im}G(\mathbf{k} + \mathbf{q}, x + i0^+)G(\mathbf{k}, -\omega + x - i0^+) + G(\mathbf{k} + \mathbf{q}, \omega + x + i0^+)\text{Im}G(\mathbf{k}, x + i0^+)]$$

It was shown that a component with the $d_{x^2-y^2}$ symmetry among various components of the spin-fluctuation-mediated interaction contributes dominantly to the pairing interaction.²⁸⁾ Therefore, in the present study, we take only the component with the $d_{x^2-y^2}$ symmetry of the pairing interaction as

$$v_d = \frac{1}{N_L^2} \sum_{\mathbf{k}} \sum_{\mathbf{k}'} \psi_d(\mathbf{k}) V(\mathbf{k} - \mathbf{k}') \psi_d(\mathbf{k}'), \quad (9)$$

with $\psi_d(\mathbf{k}) = \cos(k_x a) - \cos(k_y a)$.

The pairing susceptibility $\chi(\mathbf{q}, \omega)$, which is the irreducible part of the t -matrix, is given by

$$\chi(\mathbf{q}, \omega + i0^+) = -\frac{1}{N_L} \sum_{\mathbf{k}} \psi_d(\mathbf{k})^2 \frac{b^2 t_{\mathbf{k}}^2 t_{\mathbf{q}-\mathbf{k}}^2}{((\pi T)^2 + \omega_0^2)^2} \frac{1}{\pi} \int_{-\infty}^{\infty} dx \times [f(x) \text{Im}G(\mathbf{k}, x + i0^+)G(\mathbf{q} - \mathbf{k}, \omega - x + i0^+) - f(-x)G(\mathbf{k}, \omega - x + i0^+)\text{Im}G(\mathbf{q} - \mathbf{k}, x + i0^+)]$$

A self-energy correction due to the SC fluctuation in the t -matrix approximation is given by

$$\Sigma(\mathbf{k}, \omega + i0^+) = \frac{1}{N_L} \sum_{\mathbf{q}} \psi_d(\mathbf{q})^2 \frac{b^2 t_{\mathbf{k}}^2 t_{\mathbf{q}-\mathbf{k}}^2}{((\pi T)^2 + \omega_0^2)^2} \frac{1}{\pi} \int_{-\infty}^{\infty} dx \times [f(x)X(\mathbf{q}, x + \omega + i0^+)\text{Im}G(\mathbf{q} - \mathbf{k}, x + i0^+) - g(x)\text{Im}X(\mathbf{q}, x + i0^+)G(\mathbf{q} - \mathbf{k}, x - \omega - i0^+)]$$

with

$$X(\mathbf{q}, \omega + i0^+) = v_d^2 \chi(\mathbf{q}, \omega + i0^+) / (1 - v_d \chi(\mathbf{q}, \omega + i0^+)). \quad (12)$$

The renormalized Green's function is given by

$$\tilde{G}(\mathbf{k}, \omega + i0^+) = [G(\mathbf{k}, \omega + i0^+)^{-1} - \Sigma(\mathbf{k}, \omega + i0^+)]^{-1}. \quad (13)$$

Now we replace G in eqs. (10) and (11) by $\tilde{G}$ given in eq. (13). Then, eqs. (10)-(13) form a set of self-consistent equations for a given pairing interaction v_d . This procedure is called the self-consistent t -matrix approximation. However, it is insufficient for the present case. The reasons are as follows. The single-particle spectrum obtained above has a pseudogap, *i.e.*, suppression of the density of states near the Fermi energy in the normal state. The pseudogap suppresses the AF fluctuation and hence the pairing interaction. Thus, these effects must be treated in a fully consistent manner. To this end, we take the following scenario. We calculate $\chi_s^{(0)}(\mathbf{q}, 0)$ in eq. (8) where G is replaced by $\tilde{G}$ obtained above. Then, we find the pairing interaction v_d modified by the pseudogap through eqs. (7) and (9). We repeat the entire process until we obtain a self-consistent solution for v_d . This procedure is called the extended self-consistent t -matrix approximation.

Using the solutions obtained above, we determine the superconducting temperature T_c by the Thouless criterion,

$$1 - v_d \chi(\mathbf{0}, 0) - v_d \chi_h(\mathbf{0}, 0) = 0, \quad (14)$$

where χ_h is due to higher-order terms of the SC fluctuation, which is important in high- T_c superconducting materials because of the quasi 2-dimensionality of CuO₂

electronic systems.³²⁾ In the normal state, close to the superconducting phase, $\chi_h(\mathbf{q}, 0)$ has a sharp q -dependence, practically, $v_d\chi_h(\mathbf{q}, 0)$ is of $O(1)$ only at $\mathbf{q} \cong \mathbf{0}$ and is zero otherwise in the limit of $T \rightarrow T_c$. Thus, χ_h does not contribute to the $\mathbf{q}$ -summation in the self-energy Σ (eq.(11)) in this limit. In the present study, we simply assume that $v_d\chi_h(\mathbf{0}, 0)$ is 0.5.

We also calculate the NMR relaxation rate, $1/T_1$, using the formula³³⁾

$$\frac{1}{T_1 T} = \frac{1}{N_L} \sum_{\mathbf{q}} F_{ab}(\mathbf{q}) \lim_{\omega \rightarrow 0} \text{Im} \chi_{\mathbf{q}}^{\text{RPA}}(\omega)/\omega, \quad (15)$$

with

$$\chi_{\mathbf{q}}^{\text{RPA}}(\omega) = \chi_s^{(0)}(\mathbf{q}, \omega)/[1 - J_s(\mathbf{q})\chi_s^{(0)}(\mathbf{q}, \omega)], \quad (16)$$

$$F_{ab}(\mathbf{q}) = [A_{ab} + 2B(\cos q_x a + \cos q_y a)]^2/2 + [A_c + 2B(\cos q_x a + \cos q_y a)]^2/2, \quad (17)$$

$$A_{ab} = -170, \quad A_c = 20 \quad \text{and} \quad B = 40. \quad (18)$$

Here, $\chi_s^{(0)}(\mathbf{q}, \omega)$ is given by eq. (8), where G is replaced by $\tilde{G}$.

In actual numerical calculation, throughout the present study, we set $2t = 1.0$ (which is of $O(1\text{eV})$ in real systems), $\Delta = 2.5$ and $J_s = 0.1$. The total number of discrete points taken for the $\mathbf{q}$ -summation over the 2D first Brillouin zone is 32×32 . The ω -integral over the region from $-2\omega_0$ to $2\omega_0$ is replaced by the ω -summation of 80 discrete points.

Numerical results for the T -dependence in $1/T_1 T$ are shown in Fig. 1 for the hole-doping rate $\delta = 0.06 \sim 0.19$. At high temperatures, $1/T_1 T$ increases as T or δ decreases, due to the development of the AF fluctuation. We define T_0 as the characteristic temperature where the effects of the AF fluctuation begin to be appreciable. Explicit values of T_0 are determined by the condition that $[\frac{\partial}{\partial T}(1/T_1 T)|_{T=T_0}]/[(1/T_1 T)|_{T \rightarrow \infty, \delta=0.1}] = -2 \times 10^2$. At $\delta < 0.11$, $1/T_1 T$ has a maximum at a certain temperature denoted by T_{sg} . Curves of $1/T_1 T$ on the lower temperature sides terminate at T_c for $\delta \gtrsim 0.1$, but we have not yet obtained T_c for $\delta \lesssim 0.09$ due to the poor convergency of the numerical calculation at $T \cong T_c$. In the inset, the T -dependence of $1/T_1 T$ obtained at $\delta = 0.1$ as above (solid line) is compared with that calculated by neglecting the effects of the SC fluctuation (dashed line). We note that the SC fluctuation also becomes appreciable at $T \sim T_0$ and continues to develop along with the AF fluctuation as T decreases, while the SC fluctuation induces the pseudogap in the single-particle spectra (see Figs. 3 and 4), which suppresses the AF fluctuation. Eventually, the developed pseudogap eliminates the AF fluctuation, which leads to a sharp drop in $1/T_1 T$ at $T \lesssim T_{\text{sg}}$. Recently, Kontani showed that the Hall coefficient R_H is also enhanced by the AF fluctuation.³⁴⁾ Thus, the initial enhancement of R_H at high temperatures can be assumed to have the same origin as that of $1/T_1 T$. In this sense, we may argue that T_0 obtained in the present study corresponds to T_0 determined by R_H experiments.⁴⁾

We plot the three characteristic temperatures T_0 , T_{sg}

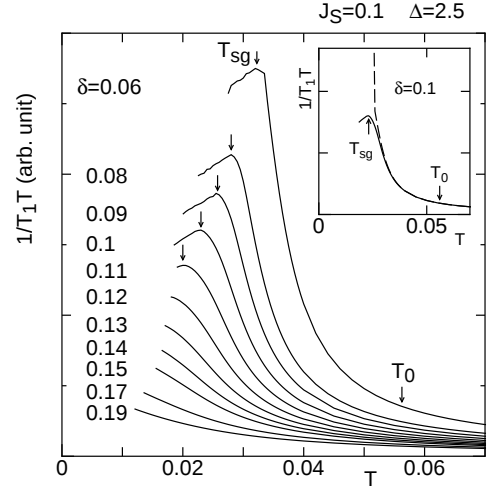


Fig. 1. T -dependences of $1/T_1 T$ obtained with $J_s = 0.1$ and $\Delta = 2.5$ for the hole-doping rate $\delta = 0.06 \sim 0.19$. In the inset, $1/T_1 T$ (solid line) is compared with that calculated by neglecting the effects of the SC fluctuation (dashed line), where $\delta = 0.1$.

and T_c as functions of δ in Fig. 2. Note that T_{sg} appears at $\delta \cong 0.11$ and increases as δ decreases, whereas T_0 appears at $\delta \cong 0.26$ and is much higher than T_{sg} . We also note that T_c has a maximum at $\delta \cong 0.11$. The dotted curve of T_c at $\delta \lesssim 0.09$ is determined by eq. (14) with the help of the extrapolation of numerical results for the T -dependence of $(1 - v_d\chi(\mathbf{0}, 0) - v_d\chi_h(\mathbf{0}, 0))$, because we had difficulty in obtaining fully convergent solutions for the self-consistent equations (7)-(13) at $T \cong T_c$ for $\delta \lesssim 0.09$. As δ decreases, the quasi-particle band narrows and the nesting effect increases, which enhances the AF fluctuation and then pushes T_0 higher. The AF fluctuation enhances the pairing interaction and then the SC fluctuation, which develops the pseudogap and then suppresses T_c in the underdoped region. T_{sg} is determined by the competition between the AF fluctuation and the SC fluctuation. The phase diagram shown in Fig. 2 accounts for essential features of the anomalous metallic phase observed in high- T_c superconducting materials.⁶⁾

The single-particle density of states, $\rho(\omega) = -\frac{1}{\pi} \text{Im} \frac{1}{N_L} \sum_{\mathbf{k}} \tilde{G}(\mathbf{k}, \omega + i0^+)$, at $T = 0.02, 0.025, 0.03$ and 0.2 with $\delta = 0.1$ where $T_0 = 0.057$ are shown in Fig. 3. At $T = 0.2$, $\rho(\omega)$ is nearly equal to that of the bare in-gap states without the effects of the SC fluctuation. At $T \lesssim T_0$, $\rho(\omega)$ decreases near the Fermi energy ($\omega = 0$) and increases at $|\omega| \gtrsim 0.05$ as T decreases. The size of the pseudogap is roughly 0.1, which corresponds to the strength of the pairing interaction of order of J_s .

Lastly, we show contour plots of the $\mathbf{k}$ -dependence on the first Brillouin zone of the single-particle spectrum at the Fermi energy $\rho(\mathbf{k}, 0) = -\frac{1}{\pi} \text{Im} G(\mathbf{k}, 0)$ with $\delta = 0.1$ at $T = 0.2$ in Fig. 4 (left) and at $T = 0.02$ in Fig. 4 (right). The single-particle spectrum $\rho(\mathbf{k}, 0)$ has a large value in bright regions, where the energy of a quasi particle with $\mathbf{k}$ is close or equal to the Fermi energy. Thus, the bright regions represent the shape of the Fermi surface. In the

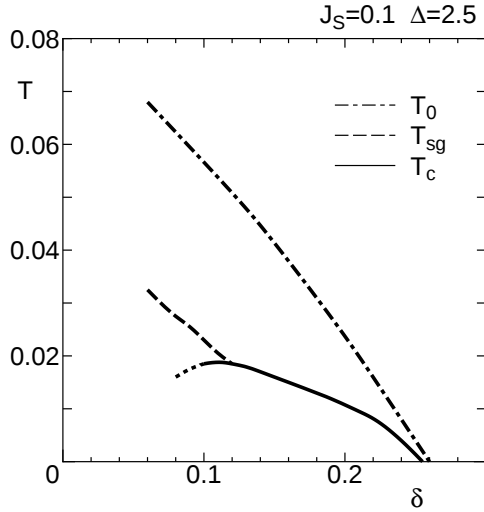


Fig. 2. δ - T phase diagram with $J_s = 0.1$ and $\Delta = 2.5$.

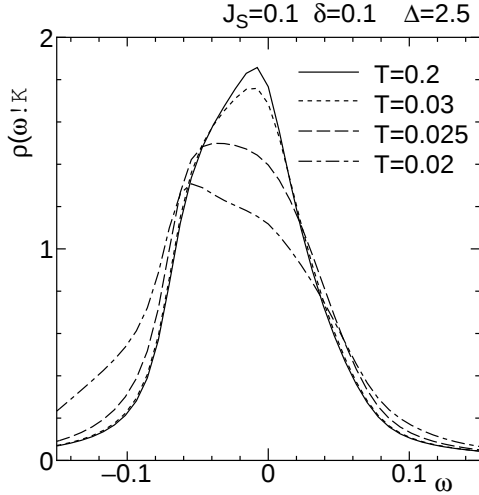


Fig. 3. Single-particle density of states at $T = 0.02, 0.025, 0.03$ and 0.2 with $\delta = 0.1$, $J_s = 0.1$ and $\Delta = 2.5$, where $T_0 = 0.057$.

dark regions, $\rho(\mathbf{k}, 0)$ is nearly zero, where the energy of a quasi particle with $\mathbf{k}$ is far from the Fermi energy. The Fermi surface exists in all directions at $T = 0.2$. As the temperature decreases, the single-particle spectra near the $[\pi, 0]$ and $[0, \pi]$ directions decrease due to the SC fluctuation with $d_{x^2-y^2}$ symmetry, and then the Fermi surface remains only near the $[\pi, \pi]$ direction at $T = 0.02$. These features are consistent with the results of ARPES experiments.⁹⁾

The present work has been supported by a Grant-in-Aid for Scientific Research from the Ministry of Education, Science, Sports and Culture.

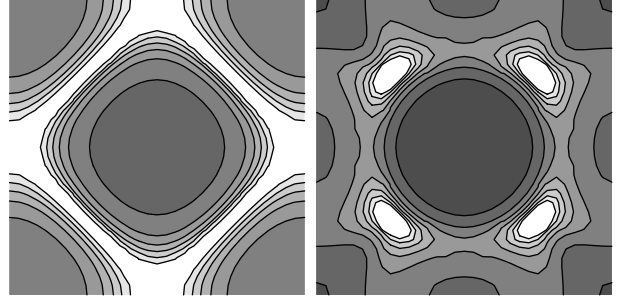


Fig. 4. Contour plots of $\mathbf{k}$ -dependences (first Brillouin zone) of the single-particle spectra at Fermi energy $\rho(\mathbf{k}, \omega = 0)$ with $\delta = 0.1$, $J_s = 0.1$ and $\Delta = 2.5$, where $T = 0.2$ (left) and $T = 0.02$ (right). Bright regions represent the shape of the Fermi surface.

185-189 (1991) 86.

- [3] K. Takenaka, K. Mizuhashi, H. Takagi and S. Uchida: Phys. Rev. B **50** (1994) 6534.
- [4] T. Nishikawa, J. Takeda and M. Sato: J. Phys. Soc. Japan **63** (1994) 1441.
- [5] T. Nakano, M. Oda, C. Manabe, N. Nomoto, Y. Miura and M. Ido: Phys. Rev. B **49** (1994) 16000.
- [6] M. Sato: Physica C **263** (1996) 271.
- [7] A. G. Loeser, Z.-X. Shen, D. S. Dessau, D. S. Marshall, C. H. Parks, P. Fournier and A. Kapitulnik: Science **273** (1996) 325.
- [8] H. Ding, T. Yokoya, J. C. Campuzano, T. Takahashi, M. Randeria, M. R. Norman, T. Mochiku, K. Kadowaki and J. Giapintzakis: Nature **382** (1996) 51.
- [9] M. R. Norman, H. Ding, M. Randeria, J. C. Campuzano, T. Yokoya, T. Takeuchi, T. Takahashi, T. Mochiku, K. Kadowaki, P. Guptasarma and D.G. Hinks: Nature **392** (1998) 157.
- [10] Y. Suzumura, Y. Hasegawa and H. Fukuyama: J. Phys. Soc. Japan **57** (1988) 2768.
- [11] H. Fukuyama: Prog. Theor. Phys. Suppl. **108** (1992) 287.
- [12] M. Randeria, N. Trivedi, A. Moreo and R.T. Scalettar: Phys. Rev. Lett. **69** (1992) 2001.
- [13] S. Koikegami and K. Yamada: J. Phys. Soc. Japan **67** (1998) 1114.
- [14] V. Emery and S. Kivelson: Nature **374** (1995) 434.
- [15] S. Doniach and M. Inui: Phys. Rev. B **41** (1990) 6668.
- [16] Q. Chen, I. Kosztin, B. Jankó and K. Levins: Phys. Rev. Lett. **81** (1998) 4708.
- [17] F. Schäfer, J. Schmalian and K. H. Bennemann: Phys. Rev. B **58** (1998) 15177.
- [18] Y. Ōno, T. Matsuura and Y. Kuroda: J. Phys. Soc. Japan **60** (1991) 3475.
- [19] P. Coleman: Phys. Rev. **B29** (1984) 3035.
- [20] B. Jin and Y. Kuroda: J. Phys. Soc. Jpn. **57** (1988) 1687.
- [21] H. Jichu, T. Matsuura and Y. Kuroda: J. Phys. Soc. Japan **59** (1990) 2820.
- [22] Y. Ōno, T. Matsuura and Y. Kuroda: J. Phys. Soc. Japan **64**, (1995) 1595.
- [23] K. Miura, T. Matsuura and Y. Kuroda: Physica **C179** (1991) 411.
- [24] D.S. Hirashima, Y. Ōno, T. Matsuura and Y. Kuroda: J. Phys. Soc. Japan **61** (1992) 649.
- [25] M. Azami, A. Kobayshi, T. Matsuura and Y. Kuroda: Physica **C259** (1996) 227.
- [26] A. Kobayashi, M. Azami, Y. Ōno, T. Matsuura, Y. Kuroda and K. Miura: Physica **C250** (1995) 307.
- [27] A. Kobayashi, Y. Ōno, T. Matsuura and Y. Kuroda: J. Phys. Soc. Japan **65** (1996) 2231.
- [28] M. Azami, T. Matsuura and Y. Kuroda: J. Phys. Soc. Japan **66** (1997) 2811.
- [29] A. Kobayashi, Y. Ōno, T. Matsuura and Y. Kuroda: Physica C **300** (1998) 287.

[1] H. Yasuoka, T. Imai and T. Shimizu: *Strong Correlation and Superconductivity*, eds. H. Fukuyama, S. Maekawa and A.P. Malozemoff (Springer-Verlag, Berlin, 1989) p. 254.

[2] J. Rossat-Mignod, L.P. Regnault, C. Vettier, P. Bourges, P. Burlet, J. Bossy, J.Y. Henry and G. Lapertot: Physica C

- [30] S. Fukagawa, A. Kobayashi, K. Miura, T. Matsuura and Y. Kuroda: J. Phys. Soc. Japan **67** (1998) 3536.
- [31] A. Kobayashi, A. Tsuruta, T. Matsuura and Y. Kuroda: J. Phys. Soc. Japan **67** (1998) 2626.
- [32] H. Sato, A. Kobayashi, A. Tsuruta, T. Matsuura and Y. Kuroda: preprint.
- [33] T. Imai: J. Phys. Soc. Japan **59** (1990) 2508.
- [34] H. Kontani: preprint.